

# High Resolution XPS Study of a Thin CoO(111) Film Grown on Co(0001)

M. Hassel

Lehrstuhl F. Physikal. Chemie I, Ruhr-Universität Bochum, Universitätsstr. 150, Bochum 44780, Germany

H.-J. Freund

Abteilung Chemische Physik, Fritz-Haber-Institut der Max-Planck-Gesell, Faradayweg 4-6, 14195 Berlin, Germany

Transition metal oxides are often used as the active components in heterogenous catalysis. Therefore the investigation of single crystal oxides as model systems is important to understand the reaction mechanisms on a microscopic level. The reactivity of a (111) surface of ionic rocksalt type structures seems to be rather high as has been established for NiO(111). The ideal (111) surface is polar, and thus unstable, which means that stabilization mechanisms must exist. Here, high resolution XPS measurements of a thin epitaxial CoO(111) film grown on CO(0001) by exposing the surface to  $\approx 10000$  L O<sub>2</sub> are reported. © 1998 American Vacuum Society.  
[S1055-5269(96)00803-1]

**Keywords:** *x-ray photoelectron spectroscopy; oxidation; cobalt oxide*

**PACS:** 79.60.Dp, 82.65.Jv, 82.80.Pv

## **SPECIMEN DESCRIPTION (Accession #00298)**

**Host Material:** Co(0001) metal

**Host Material Characteristics:** homogeneous; solid; single crystal; conductor; metal

**Chemical Name:** cobalt

**Host Composition:** Co

**Form:** single crystal

**Structure:** (0001) hexagonal close packed

**As Received Condition:** single crystal as grown

**Analyzed Region:** (0001) surface

**Ex Situ Preparation/Mounting:** single crystal cut in (0001) direction and polished, then spot-welded on the sample holder

**In Situ Preparation:** ion sputter cleaning and annealing

**Charge Control:** no charge control necessary as host material is metallic

**Temp. During Analysis:** 300 K

**Pressure During Analysis:**  $<1 \times 10^{-7}$  Pa

## **SPECIMEN DESCRIPTION (Accession #00299)**

**Host Material:** CoO(111) on Co

**Host Material Characteristics:** homogeneous; solid; single crystal; dielectric; inorganic compound; thin film

**Chemical Name:** cobalt oxide

**Host Composition:** Co, O

**Form:** thin film

**Structure:** CoO(111)

**History & Significance:** The analyzed sample was grown by oxidation of Co(0001) for 3 h with a background pressure of  $10^{-6}$  mbar. During this time the sample was slowly heated up to 450 K. After this it was annealed for 1 h without oxygen background pressure (Ref. 1).

**Accession #s** 00298, 00299

**Technique:** XPS

**Host Material:** #00298: Co(0001) metal; #00299: CoO(111) on Co

**Instrument:** Leybold-Heraeus EA 11

**Major Elements in Spectrum:** Co, O

**Minor Elements in Spectrum:** none

**Printed Spectra:** 6

**Spectra in Electronic Record:** 6

**Spectral Category:** comparison

**Original Submission:** 12/04/95

**Accepted for Publication:** 8/13/96

**As Received Condition:** not specified

**Analyzed Region:** oxidized host material

**Ex Situ Preparation/Mounting:** single crystal cut in (0001) direction and polished, then spot-welded to the manipulator

**In Situ Preparation:** no additional preparation after oxide growth (see History and Significance)

**Charge Control:** no charge control necessary as host material is metallic

**Temp. During Analysis:** 300 K

**Pressure During Analysis:**  $<1 \times 10^{-7}$  Pa

## **INSTRUMENT DESCRIPTION**

**Manufacturer and Model:** Leybold-Heraeus EA 11

**Analyzer Type:** spherical sector

**Detector:** 2 multichannel plates

## **INSTRUMENT PARAMETERS COMMON TO ALL SPECTRA**

### ■ Spectrometer

**Analyzer Mode:** constant pass energy

**Throughput ( $T = E^N$ ):**  $N = -1$

**Excitation Source Window:** 1.5  $\mu\text{m}$  Al window

**Excitation Source:** Al  $K_{\alpha}$  monochromatic

**Source Energy:** 1486.6 eV

**Source Strength:** 450 W

**Analyzer Width:** 3000  $\mu\text{m} \times 3000 \mu\text{m}$

**Signal Mode:** multichannel direct

### ■ Geometry

**Incident Angle:** 45°

**Source to Analyzer Angle:** 45°

**Emission Angle:** 0°

Specimen Azimuthal Angle: 0°  
 Acceptance Angle from Analyzer Axis: 1.5°  
 Analyzer Angular Acceptance Width: 3° × 3°

■ **Ion Gun**

Manufacturer and Model: Leybold-Heraeus IQE 12/38

Energy: 500 eV

Current: 10 μA

Current Measurement Method: biased stage

Sputtering Species: Ne

Raster Size: 10000 μm × 10000 μm

Incident Angle: 45°

Polar Angle: 45°

Azimuthal Angle: 0°

**DATA ANALYSIS METHOD**

Energy Scale Correction: energy scale calibration to Fermi level of Co metal

**ACKNOWLEDGMENTS**

Several agencies have supported our work: Deutsche Forschungsgemeinschaft, Ministerium für Wissenschaft und Forschung des Landes NRW, and Fonds der Chemischen Industrie.

**REFERENCES**

1. M. Hassel and H.-J. Freund, Surf. Sci. **325**, 163 (1995).

**SPECTRAL FEATURES TABLE**

Spectrum ID #	Element/Transition	Peak Energy (eV)	Peak Width FWHM (eV)	Peak Area	Sensitivity Factor	Concentration (at. %)	Peak Assignment
00299-02	O 1s	530.0	1.0	...	...	...	CoO(111)
00299-02	O 1s	531.8	1.3	...	...	...	OH groups
00299-03	Co 2p <sub>1/2</sub>	796.8	4.5	...	...	...	CoO(111)
00299-03	Co 2p <sub>3/2</sub>	780.6	5.0	...	...	...	CoO(111)
00299-04	Co 3s	101.4	5.0	...	...	...	CoO(111)
00299-04	Co 3p	59.4	4.0	...	...	...	CoO(111)
00299-05	Co/O valence band	1.4	5.0	...	...	...	CoO(111)

**ANALYZER CALIBRATION TABLE**

Spectrum ID #	Element/Transition	Peak Energy (eV)	Peak Width FWHM (eV)	Sensitivity Factor	Concentration (at. %)	Peak Assignment
...	...	...	...	...	...	...


**Comment to Analyzer Calibration Table:** The energy scale was calibrated by determining the Fermi edge of the Co(0001) substrate.

**GUIDE TO FIGURES**


Spectrum (Accession) #	Sample Voltage*	Multiplier	Baseline	Comment #
298-1	0	1.000	0	-
299-1	0	1.000	0	1
298-2	0	1.000	0	1
299-3	0	1.000	0	1
299-4	0	1.000	0	1
299-5	0	1.000	0	1

\* Sample voltage due to charging unless otherwise noted.


1. Peak energies were referenced to Fermi level of Co metal substrate which could be measured through thin oxide (see 299-5).

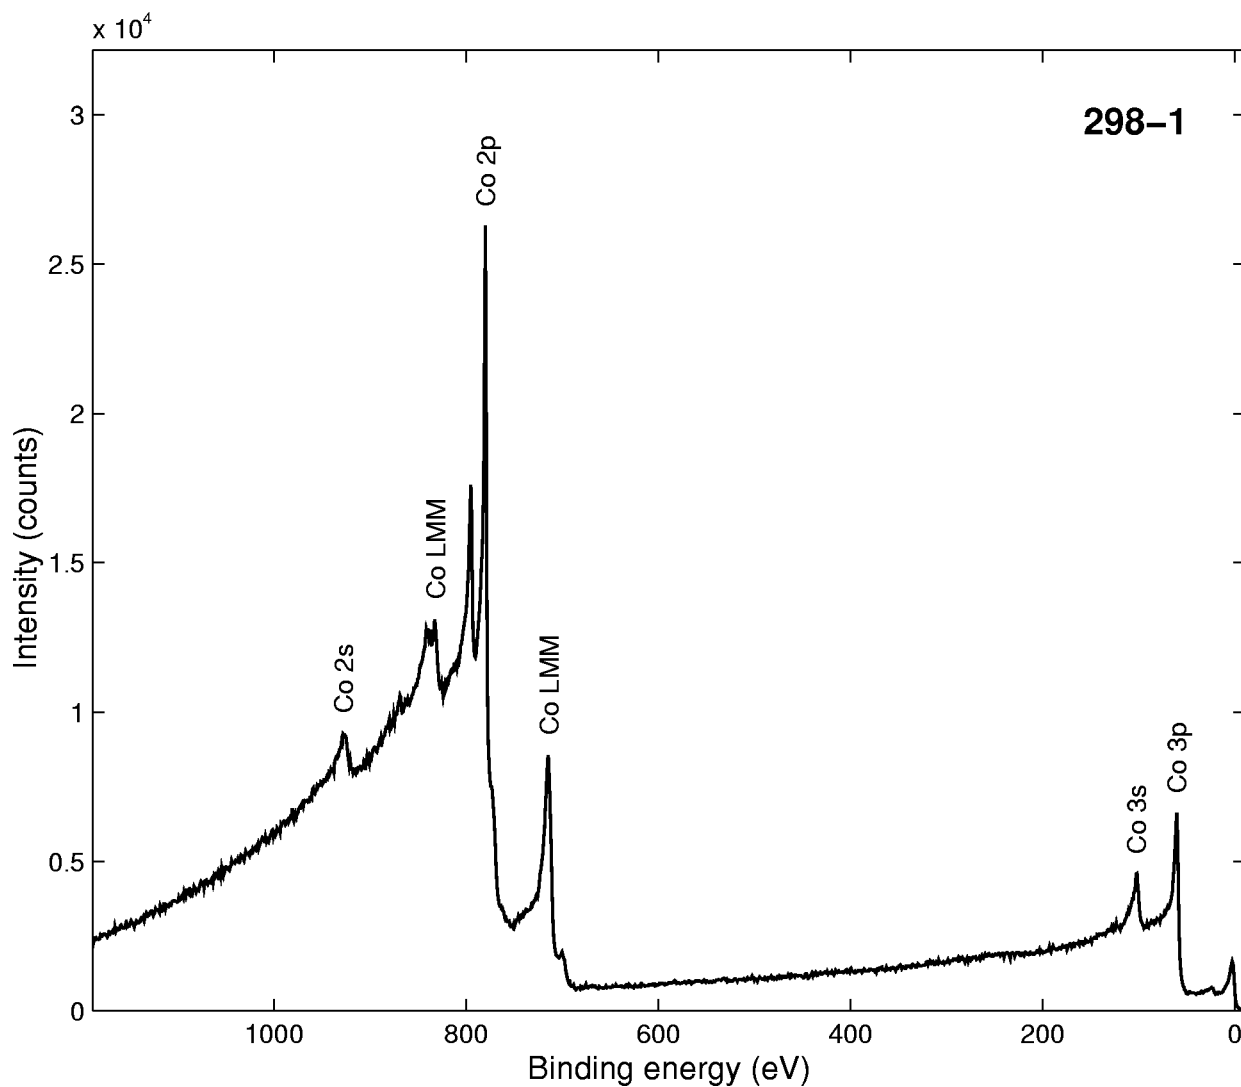


<b>Accession #</b>	<b>00298-01</b>
<b>Host Material</b>	Co(0001) metal
<b>Technique</b>	XPS
<b>Spectral Region</b>	survey
<b>Instrument</b>	Leybold-Heraeus EA 11
<b>Excitation Source</b>	Al $K_{\alpha}$ monochromatic
<b>Source Energy</b>	1486.6 eV
<b>Source Strength</b>	450 W
<b>Source Size</b>	not specified
<b>Analyzer Type</b>	spherical sector
<b>Incident Angle</b>	45°
<b>Emission Angle</b>	0°
<b>Analyzer Retard Ratio</b>	4
<b>Analyzer Resolution</b>	0.125 eV
<b>Total Signal Accumulation Time</b>	not specified
<b>Total Elapsed Time</b>	330 s
<b>Number of Scans</b>	5
<b>Comment</b>	survey of the clean Co single crystal

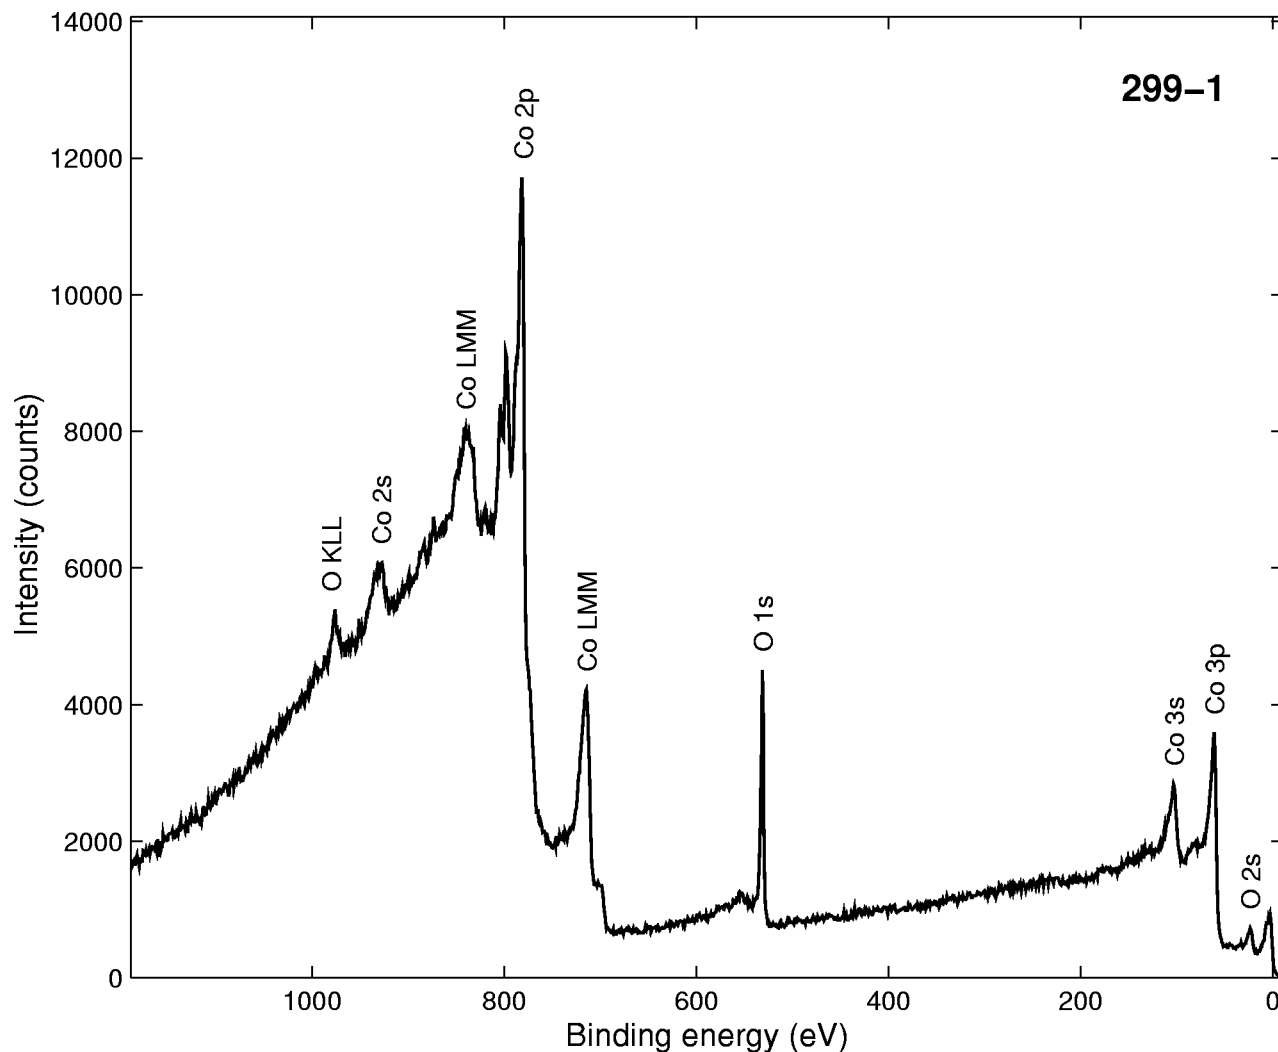


<b>Accession #</b>	<b>00299-01</b>
<b>Host Material</b>	CoO(111) on Co
<b>Technique</b>	XPS
<b>Spectral Region</b>	survey
<b>Instrument</b>	Leybold-Heraeus EA 11
<b>Excitation Source</b>	Al $K_{\alpha}$ monochromatic
<b>Source Energy</b>	1486.6 eV
<b>Source Strength</b>	450 W
<b>Source Size</b>	not specified
<b>Analyzer Type</b>	spherical sector
<b>Incident Angle</b>	45°
<b>Emission Angle</b>	0°
<b>Analyzer Retard Ratio</b>	4
<b>Analyzer Resolution</b>	0.125 eV
<b>Total Signal Accumulation Time</b>	not specified
<b>Total Elapsed Time</b>	330 s
<b>Number of Scans</b>	5
<b>Comment</b>	survey of the oxidized Co single crystal

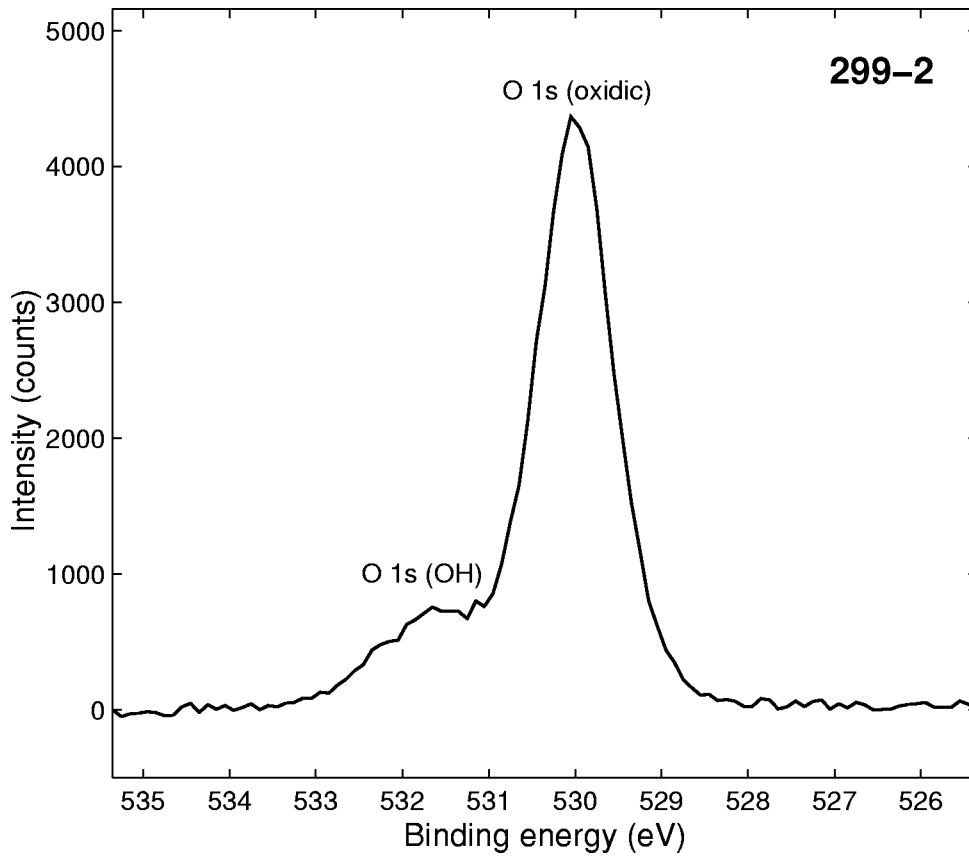


■ **Accession #:** 00299-02  
 ■ **Host Material:** CoO(111) on Co  
 ■ **Technique:** XPS  
 ■ **Spectral Region:** O 1s  
 Instrument: Leybold-Heraeus EA 11  
 Excitation Source: Al  $K_{\alpha}$  monochromatic  
 Source Energy: 1486.6 eV  
 Source Strength: 450 W  
 Source Size: not specified  
 Incident Angle: 45°  
 Analyzer Type: spherical sector  
 Analyzer Pass Energy: 25.2 eV  
 Analyzer Resolution: 0.3 eV  
 Emission Angle: 0°  
 Total Signal Accumulation Time: not specified  
 Total Elapsed Time: 900 s  
 Number of Scans: 50  
 Comment: oxidized Co single crystal

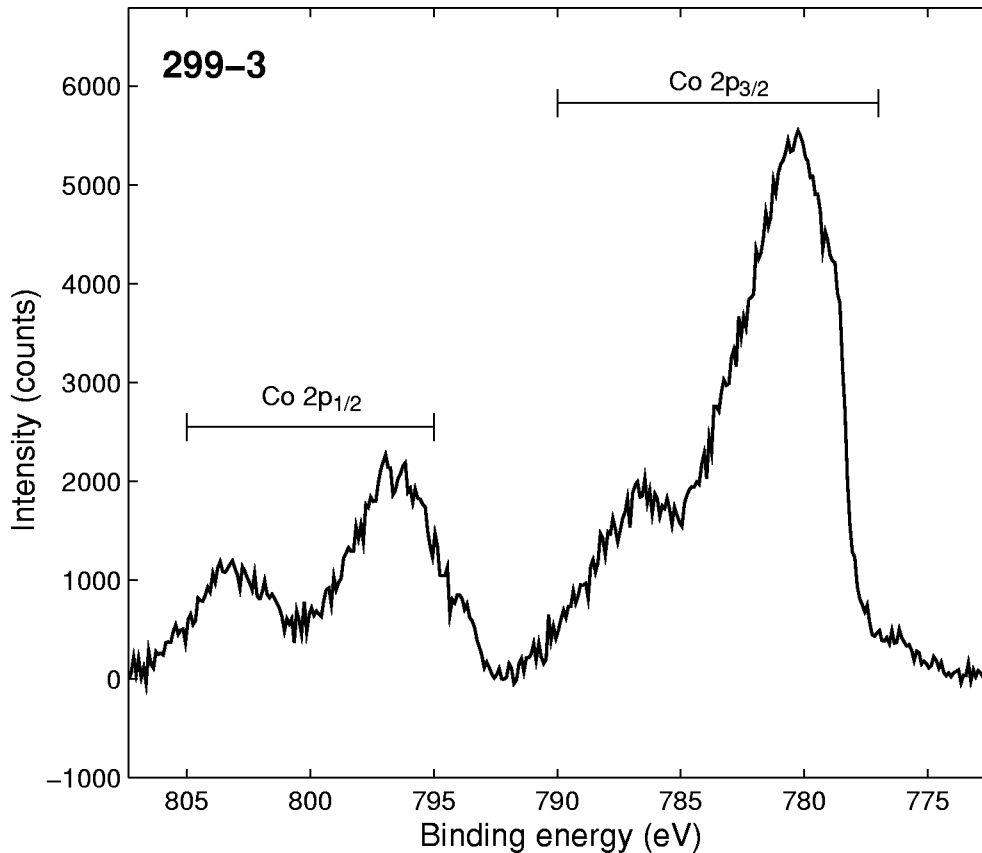

■ **Accession #:** 00299-03  
 ■ **Host Material:** CoO(111) on Co  
 ■ **Technique:** XPS  
 ■ **Spectral Region:** Co  $2p_{1/2}$ ; Co  $2p_{3/2}$   
 Instrument: Leybold-Heraeus EA 11  
 Excitation Source: Al  $K_{\alpha}$  monochromatic  
 Source Energy: 1486.6 eV  
 Source Strength: 450 W  
 Source Size: not specified  
 Incident Angle: 45°  
 Analyzer Type: spherical sector  
 Analyzer Pass Energy: 25.2 eV  
 Analyzer Resolution: 0.3 eV  
 Emission Angle: 0°  
 Total Signal Accumulation Time: not specified  
 Total Elapsed Time: 2150 s  
 Number of Scans: 50  
 Comment: oxidized Co single crystal

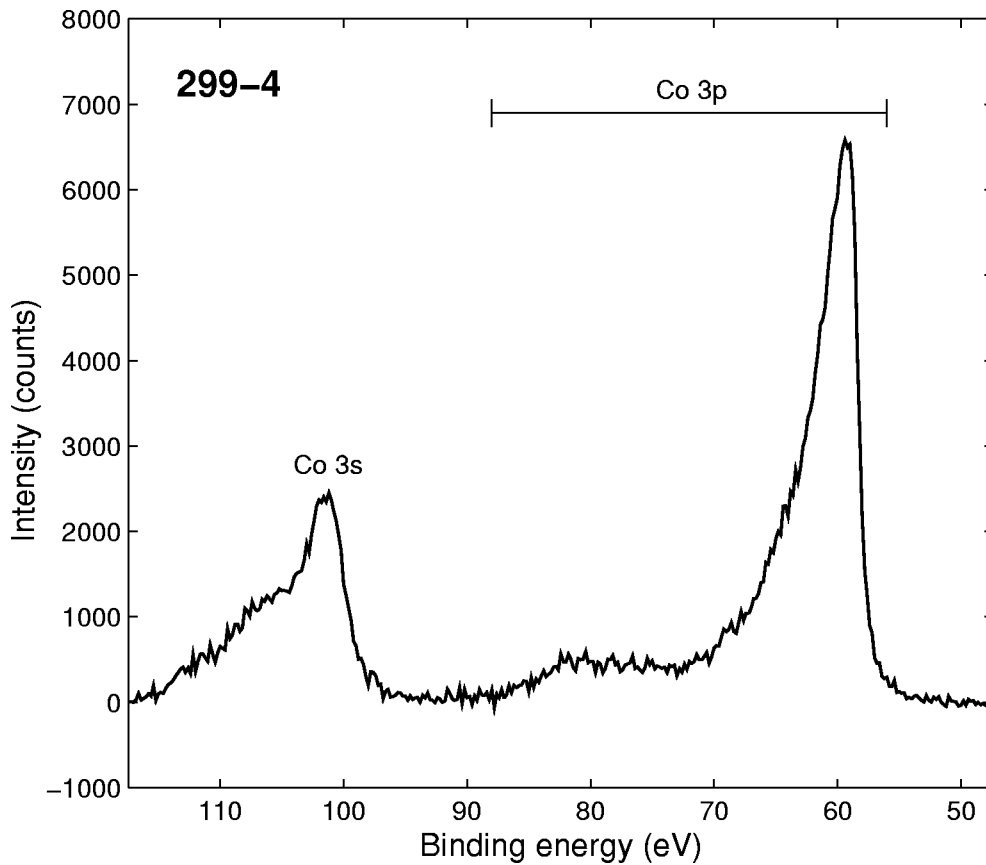

■ **Accession #:** 00299-04  
 ■ **Host Material:** CoO(111) on Co  
 ■ **Technique:** XPS  
 ■ **Spectral Region:** survey  
 Instrument: Leybold-Heraeus EA 11  
 Excitation Source: Al  $K_{\alpha}$  monochromatic  
 Source Energy: 1486.6 eV  
 Source Strength: 450 W  
 Source Size: not specified  
 Analyzer type: spherical sector  
 incident Angle: 45°  
 Emission Angle: 0°  
 Analyzer Retard Ratio: 4  
 Analyzer Resolution: 0.125 eV  
 Total Signal Accumulation Time: not specified  
 Total Elapsed Time: 330 s  
 Number of Scans: 5  
 Comment: survey of the oxidized Co single crystal

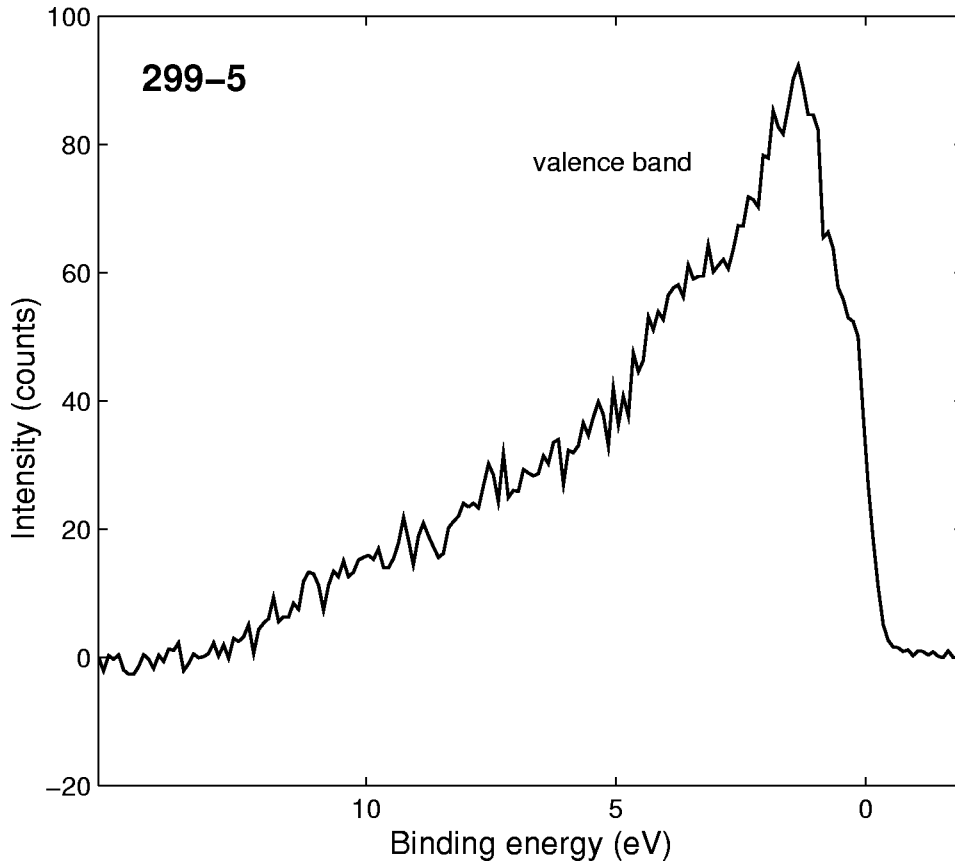

■ **Accession #:** 00299-05  
 ■ **Host Material:** CoO(111) on Co  
 ■ **Technique:** XPS  
 ■ **Spectral Region:** Co valence band; O valence band  
 Instrument: Leybold-Heraeus EA 11  
 Excitation Source: Al  $K_{\alpha}$  monochromatic  
 Source Energy: 1486.6 eV  
 Source Strength: 450 W  
 Source Size: not specified  
 Incident Angle: 45°  
 Analyzer Type: spherical sector  
 Analyzer Pass Energy: 25.2 eV  
 Analyzer Resolution: 0.3 eV  
 Emission Angle: 0°  
 Total Signal Accumulation Time: not specified  
 Total Elapsed Time: 4400 s  
 Number of Scans: 200  
 Comment: oxidized Co single crystal